

Microarticle

Random lasing in a short Er-doped artificial Rayleigh fiber

S.M. Popov^{a,*}, O.V. Butov^b, A.P. Bazakutsa^b, M.Yu. Vyatkin^a, Yu.K. Chamorovskii^a, A.A. Fotiadi^{c,d}^a Kotelnikov Institute of Radioengineering and Electronics (Fryazino Branch) Russian Academy of Science, 141190, Vvedenskogo Sq. 1, Fryazino, Russia^b Kotelnikov Institute of Radioengineering and Electronics Russian Academy of Science, 125009, Mokhovaya 11 bld. 7, Moscow, Russia^c Electromagnetism and Telecommunication Department, University of Mons, Mons B-7000, Belgium^d Ulyanovsk State University, 42 Leo Tolstoy Street, Ulyanovsk 432970, Russian Federation

ARTICLE INFO

Keywords:

Random fiber laser

Fiber Bragg gratings array

Dynamical population inversion grating

ABSTRACT

We report on random lasing observed with 5-m-long Er-doped fiber comprising an array of weak fiber Bragg gratings (FBGs) inscribed in the fiber core and uniformly distributed over the whole fiber length. The laser design ensures domination of dynamical population inversion grating over the FBGs in total distributed feedback enabling laser stabilization and nonlinear laser line filtering of the natural laser Lorentzian linewidth down to sub-300-Hz range, both observed in the experiment.

Random fiber lasers have recently become a topic of great interest for researchers around the world due to the fact that they are able to produce light with unique performance characteristics without imposing stringent requirements on the optical resonator [1–7]. Traditionally, random fiber lasers are implemented using long (10–100 km) Raman or Brillouin fiber amplifiers possessing inhomogeneous gain line broadening and comprising weak stationary (“frozen”) scattering centers uniformly distributed over the fiber length (Rayleigh scattering). Current trends in random fiber lasers are associated with transition to short laser configurations based on short (~100 m) FBG array fibers referred to as artificial Rayleigh fibers (the term accepted in distributed fiber sensing) [8,9] and/or using active fibers [10–17]. In comparison with traditional random fiber lasers, the use of short Rayleigh fibers provides much lower spectral selectivity to the generated light; therefore, in general, such lasers operate much broader laser linewidths. In random lasers comprising the active fibers the distributed dynamic population inversion gratings inscribed by the lasing radiation in the active media may have a reverse effect on the writing laser radiation via a feedback they provide [18]. The integrated reflectivity induced by the dynamical gratings in active fibers could be as high as 8% [17]. Factually, during the lasing they are reformatting the random laser cavity initially formed by the stationary scattering centers and may drastically affect the laser dynamics [15–17]. Recently, some of us have reported random lasing based on Brillouin gain and combined action of stationary and dynamic reflecting structures demonstrating an unexpected narrowing of the laser line down to 10 kHz [19,20]. In that laser system, the effects of stationary random lasing and nonlinear laser line filtering provided by the dynamical population inversion grating

occurred in different fibers, i.e. in 100-m length of a single-mode artificial Rayleigh fiber and a 1-m length of Er-doped fiber, respectively. Without the active fiber segment, the laser operated several spectral components. In this paper, we go two steps further demonstrating random lasing with sub-300-Hz laser Lorentzian linewidth achieved (i) in a single 5-m long artificial Rayleigh Er-doped fiber and (ii) under the population inversion amplification possessing inhomogeneous gain line broadening. In contrast to previous works on random lasing in Er-doped fibers comprising multiple discrete FBGs [10–14], in our experiment we use numerous gratings inscribed over the whole Er-doped fiber length and exhibiting very low individual reflectivity. Such laser design ensures domination of the reflectivity imposed by dynamical population inversion grating over weak stationary reflection centers, thus enabling effective nonlinear filtering immediately in the fiber cavity and laser Lorentzian linewidth narrowing down to sub-300-Hz frequency range.

The experimental configuration of the random laser is shown in Fig. 1(a). The artificial Er-doped Rayleigh fiber (FBG array fiber) has been fabricated from the preform using the IRE fiber drawing tower equipped with an KrF-excimer laser. The fiber preform with Er³⁺-doped germanium-free silica core has been manufactured by the surface plasma chemical vapor deposition (SPCVD) method [21]. The refractive index fiber profile is provided by adding aluminum into the core silica glass network. The fiber core diameter is 6 μm, cladding diameter is 125 μm, core/cladding refractive index step difference is ~0.0045, numerical aperture is ~0.11, peak light absorption at 976 nm and 1530 nm is 13 and 20 dB/m, respectively. Multiple weak uniform 1-cm-long FBGs with an individual peak reflectivity of ~0.00003% at ~1547.6 nm are inscribed in the fiber core by the KrF- laser at

* Corresponding author.

E-mail address: sergei@popov.eu.org (S.M. Popov).

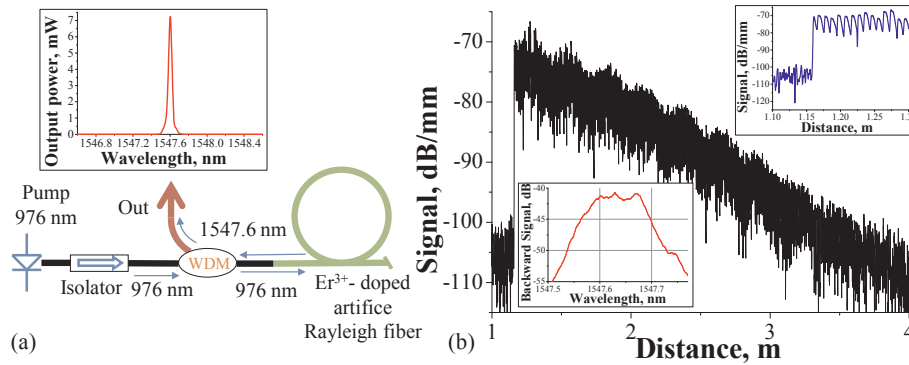


Fig. 1. Experimental setup (a) and laser optical spectrum (a, inset). The OFDR trace of the Er-doped artificial Rayleigh fiber (~ 60 m) (b), a zoom of the OFDR trace (b, top); Reflectivity spectrum of the fiber (~ 3 m) (b, bottom).

248 nm (the pulse energy density is ~ 400 mJ/cm², pulse duration is 10 ns, repetition rate is 10 Hz) through a phase mask with a grating's pitch of 1070 nm, in-situ, one-by-one, immediately during the fiber drawing process (the drawing speed is 6 m/min) [9]. All FBGs are uniformly distributed over the fiber length with 100% fill factor (i.e. without an overlap and gap between the neighboring gratings). The total reflectivity measured with 3-m fiber length exhibits a $\sim 0.01\%$ peak at 1547.6 nm with ~ 0.2 nm spectrum FWHM width (Fig. 1(b, bottom inset)). The fiber longitudinal profile measured at 1547.6 nm by the optical frequency domain reflectometer (OFDR) Luna 4400 is shown in Fig. 1(b). The observed regularity with the period of ~ 1 /cm highlights the inscribed FBG array (Fig. 1(b, top inset)). It is worth noting that due to the phase-based principle of the OFDR, a non-coherent luminescence (noise) induced by the interrogating signal does not make a significant contribution to the recorded traces. However, only first ~ 4 m of the fiber are observable in Fig. 1(b) due to high absorption at the testing wavelength. The artificial Er-doped Rayleigh fiber (FBG array fiber) is pumped at 976 nm through a wavelength-division-multiplexer (WDM) by 650mW pump laser diode (Gooch & Housego). The laser radiation is monitored through the second WDM arm. To avoid backreflections two free ends of the fiber configuration (i.e. belonging to WDM and Rayleigh fiber) are angled cleaved. The laser optical spectrum is centered at ~ 1547.6 nm as shown in Fig. 1(a, inset).

Fig. 2(a) shows the laser threshold pump power as a function of the fiber length. The minimal laser threshold level (~ 100 mW) is observed with a long fiber (> 5 m), while it increases up to 370mW for 3-m fiber. Fig. 2 (a, inset) shows the output laser power as a function of the pump

power demonstrating the maximal conversion efficiency of 2.5% achieved at 300 mW. The recorded traces of the laser output power, like shown in Fig. 2 (b), exhibit small fluctuations around the average level highlighting behavior typical for random lasing [1]. The minimal standard deviation of the output power fluctuation is observed at level of ~ 250 mW and estimated to be $\sim 2\%$. This laser operation essentially differs from pulsations commonly observed with heavily Er-doped fiber lasers [22].

Fig. 2(b, inset) shows the self-heterodyne RF spectrum of laser radiation measured by RF analyzer (FSH8, Rohde & Schwarz) with an unbalanced Mach-Zehnder interferometer comprising ~ 40 MHz electro-optic modulator and ~ 50 km delay fiber. The recorded spectrum exhibits oscillations in the wings demonstrating that the laser coherence length is longer than the delay fiber [23]. There are two kinds of noise contributing to the spectrum: the laser white frequency noise providing a natural (Lorentzian) laser linewidth, and the $1/f$ frequency noise resulting in the approximate Gaussian linewidth [24]. The main cause of the $1/f$ frequency noise in fiber lasers is temperature fluctuations induced by pump intensity noise [25]. In the considered sub-coherent regime, the $1/f$ noise is partially filtered out from the measured spectrum [26], so we can just estimate the laser Gaussian linewidth to be between ~ 850 Hz and ~ 4 kHz. Here, the lower limit is determined by the measured 3-dB spectrum width (~ 1200 Hz) with the deconvolution factor of $\sqrt{2}$, while the upper limit is set by the resolution linked to the delay fiber length. The measured 20-dB spectrum width (~ 5800 Hz) is weakly affected by the Gaussian noise and in sub-coherent regime overestimates the FWHM Lorentzian linewidth (the deconvolution factor is $2\sqrt{99}$) [27]. Therefore, the natural Lorentzian

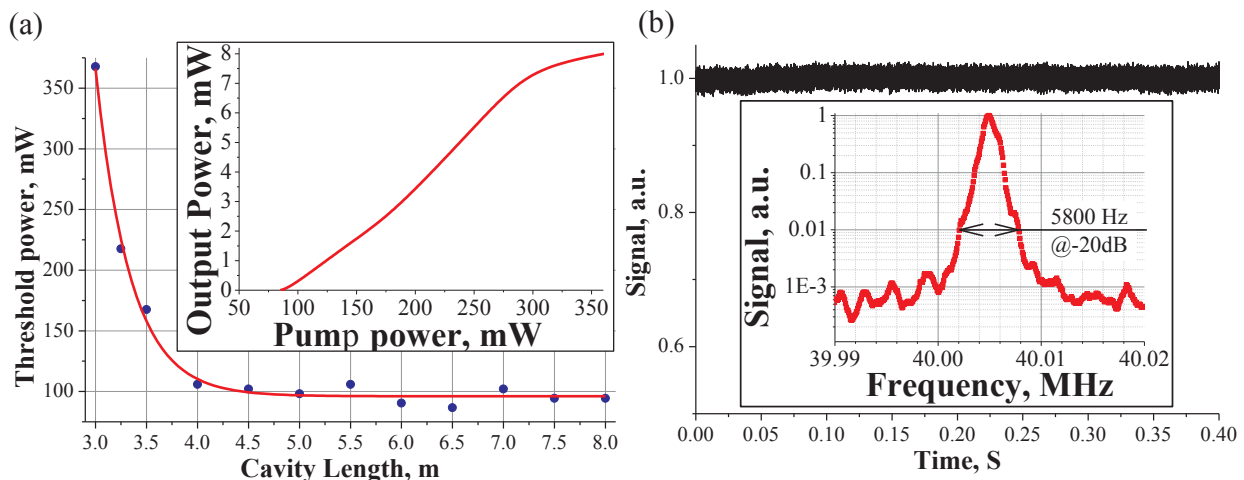


Fig. 2. Laser characteristics: the threshold pump power as a function of the fiber length (a), the output power as a function of the pump power (a, inset), a typical oscilloscope trace (b) and self-heterodyne spectrum (b, inset).

linewidth is found to be narrower than ~ 290 Hz. Note, the $1/f$ noise could be eliminated by using low-noise pumping [25].

We believe that such strong suppression of the laser Lorentzian linewidth is caused by the dynamical population inversion grating inscribed immediately in the random fiber cavity during lasing. The observed laser features differ drastically from the lasing of a few spectral components reported earlier with the Er-doped configurations comprising discrete FBGs with dominating stationary reflectivity [10].

In summary, we have observed random lasing in a short Er-doped artificial Rayleigh fiber pumped by the laser diode. The lasing is achieved due to the population inversion gain and feedback caused by weak FBGs uniformly distributed over the fiber length. The laser design ensures domination of the reflectivity imposed by dynamical population inversion grating over the stationary FBGs enabling laser stability and laser Lorentzian linewidth narrowing down to ~ 290 Hz, while the Gaussian linewidth is kept < 4 kHz. The proposed random laser is a simple, compact, and cost-effective solution for many practical applications.

We thank the IRE staff for manufacturing the preform (Prof. K.M. Golant, V.A. Aksenov) and drawing the experimental fiber (I.L. Vorobyev, V.V. Voloshin, A.O. Kolosovskii). The work was carried out within the framework of the state task and partially supported by the Russian Foundation for Basic Research (RFBR) grant 17-07-01388 A. The work of A.A.F is supported by Russian Science Foundation grant 18-12-00457 and RFBR grant 18-42-732001 r_mk.

Declaration of Competing Interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

References

- [1] Fotiadi AA, Kiyon RV. Cooperative stimulated Brillouin and Rayleigh backscattering process in optical fiber. *Opt Lett* 1998;23:1805–7.
- [2] Fotiadi AA. Random lasers: an incoherent fibre laser. *Nature Photon* 2010;4:204–5.
- [3] Turitsyn SK, Babin SA, El-Tajer AE, Paul Harper DV, Churkin SI, Kablukov JD, et al. Random distributed feedback fibre laser. *Nature Photon* 2010;4:231–5.
- [4] Fotiadi AA, Lobach I, Mégret P. Dynamics of ultra-long Brillouin fiber laser. *Proc SPIE* 2012;8601:86011K.
- [5] Turitsyn SK, Babin SA, Churkin DV, Vatik ID, Nikulin M, Podivilov EV. Random distributed feedback fibre lasers. *Phys Rep* 2014;542:133–93.
- [6] Churkin DV, Sugavanam S, Vatik ID, Wang Z, Podivilov EV, Babin SA, et al. Recent advances in fundamentals and applications of random fiber lasers. *Adv Opt Photon* 2015;7:516–69.
- [7] Budarnykh AE, Lobach IA, Zlobina EA, Velmskin VV, Kablukov SI, Semjonov SI, et al. Raman fiber laser with random distributed feedback based on a twin-core fiber. *Opt Lett* 2018;43:567–70.
- [8] Askins C, Putnam M, Williams G, Friebele E. Stepped-wavelength optical-fiber bragg grating arrays fabricated in line on a draw tower. *Opt Lett* 1994;19:147–9.
- [9] Zaitsev IA, Butov OV, Voloshin VV, Vorob'ev IL, Vyatkin MYu, Kolosovskii AO, et al. Optical fiber with distributed bragg type reflector. *J Comm Tech Elec* 2016;61:639–45.
- [10] Lizarraga N, Puente NP, Chaikina EI, Leskova TA, Mendez ER. Single-mode Er-doped fiber random laser with distributed bragg grating feedback. *Opt Express* 2009;17:395–404.
- [11] Bliokh Y, Chaikina EI, Lizárraga N, Méndez ER, Freilikher V, Nori F. Disorder-induced cavities, resonances, and lasing in randomly layered media. *Phys Rev B* 2012;86:054204.
- [12] Ye J, Xu J, Zhang H, Zhou P. Powerful narrow linewidth random fiber laser. *Photon Sensors* 2017;7:82–7.
- [13] Popov SM, Butov OV, Chamorovskiy YK, Isaev VA, Kolosovskiy AO, Voloshin VV, et al. Brillouin lasing in single-mode tapered optical fiber with inscribed fiber bragg grating array. *Results Phys* 2018;9:625–7.
- [14] Abdullina S, Vlasov A, Lobach I, Belai O, Shapiro D, Babin S. Single-frequency yb-doped fiber laser with distributed feedback based on a random FBG. *Laser Phys Lett* 2016;13:075104.
- [15] Lobach IA, Kablukov SI, Podivilov EV, Fotiadi AA, S.A. Babin Fourier synthesis with single-mode pulses from a multimode laser. *Opt Lett* 2015;40:3671–4.
- [16] Drobyshch RV, Lobach IA, Podivilov EV, Kablukov SI. Spectral characterization technique of self-organized distributed feedback in a self-sweeping fiber laser. *Opt Express* 2019;27:21335–46.
- [17] Lobach IA, Drobyshch RV, Fotiadi AA, Podivilov EV, Kablukov SI, Babin SA. Open-cavity fiber laser with distributed feedback based on externally or self-induced dynamic gratings. *Opt Lett* 2017;42:4207–10.
- [18] Stepanov S, Fotiadi AA, Mégret P. Effective recording of dynamic phase gratings in Yb-doped fibers with saturable absorption at 1064nm. *Opt Express* 2007;15:8832–7.
- [19] Popov SM, Chamorovsky YuK, Mégret P, Zolotovskii IO, Fotiadi AA. Brillouin random lasing in artifice rayleigh fiber. *European Conference on Optical Communication (ECOC)*. 2015. p. 1–3.
- [20] Popov SM, Butov OV, Chamorovski YK, Isaev VA, Mégret P, Korobko DA, et al. Narrow linewidth short cavity brillouin random laser based on bragg grating array fiber and dynamical population inversion gratings. *Results Phys* 2018;9:806–8.
- [21] Kholodkov A, Golant K. Er 3+ ion photoluminescence in silicate glasses obtained by plasma-chemical deposition in a low-pressure microwave discharge. *Tech Phys* 2005;50:719–26.
- [22] Smirnov AM, Bazakutsa AP, Chamorovskiy YuK, Nepochenko IA, Dorofeenko AV, Butov OV. Thermal switching of lasing regimes in heavily doped Er³⁺ fiber lasers. *ACS Photon* 2018;5:5038–46.
- [23] Richter LE, Mandelberg HI, Kruger MS, Mcgrath PA. Linewidth determination from self-heterodyne measurements with subcoherence delay times. *IEEE J Quantum Electron* 1986;22:2070–4.
- [24] Mercer LB. $1/f$ frequency noise effects on self-heterodyne linewidth measurements. *J Lightwave Technol* 1991;9:485–93.
- [25] Horak P, Voo NY, Ibsen M, Loh WH. Pump-noise-induced linewidth contributions in distributed feedback fiber lasers. *IEEE Photon Technol Lett* 2006;18:998–1000.
- [26] Horak P, Loh WH. On the delayed self-heterodyne interferometric technique for determining the linewidth of fiber lasers. *Opt Express* 2006;14:3923–8.
- [27] Yu P. A novel scheme for hundred-hertz linewidth measurements with the self-heterodyne method. *Chin Phys Lett* 2013;30:084208.